

Ascend Sealing Technology Compound: H10190BL

Ascend Sealing has developed Hydrogenated Nitrile rubber (HNBR) to be the most cost-effective compound, without sacrificing performance for general usage. HNBR is one of the most popular material for sealing application. We specially formulated H10190BL for good resistance to common lubricants and oils with ideal mechanical properties. As for general purpose, H10190BL is a sulfur-cured compound with good balance between physical and chemical resistance.

Service Temperature: -31°F to 302°F (-35°C to 150°C)

Ascend Sealing provides a wide range of HNBRs. For additional technical support, please contact us at [customer\\_service@ascendsealing.com](mailto:customer_service@ascendsealing.com).

### **Compatible**

- Vegetable oils
- Water and steam to 150°C (302°F)
- Petroleum based oils and fuels
- Silicone oils and greases
- Ethylene glycol
- Dilute acids, bases and salt solutions to moderate temperatures
- Aliphatic hydrocarbons

### **Incompatible**

- Esters
- Strong acids
- Ketones
- Ethers
- Chlorinated hydrocarbons

#### **Ascend Sealing Technology Inc.**

1211 Alderwood Ave, Sunnyvale, CA 94089

Tel: (408) 962-0126 | Fax: (408) 962-0485

Email: [customer\\_service@ascendsealing.com](mailto:customer_service@ascendsealing.com)

<https://www.ascendsealing.com/>

## Physical Properties

MATERIAL :	HNBR
COMPOUND :	H10190BL
SPEC. :	ASTM D2000 M4DH910 A26 B36 EO16 EO36 F17 Z1
COLOR :	BLACK

	<u>Original Physical Properties</u>	<u>Requirements</u>	<u>Results</u>
	Hardness, (Shore A) (ASTM D2240-05)	90±5	90
	Tensile Strength, psi(MPa) (ASTM D412-06a)	1450(10)(min)	3184(21.96)
	Elongation, (%) (ASTM D412-06a)	100(min)	153
	Modulus at 100%, psi(MPa) (ASTM D412-06a)		2176(15.01)
	Density, (Mg/m <sup>3</sup> ) (CNS 5341-96, Method A)		1.30
<u>A26</u>	<u>Heat Age, 70 Hrs @ 150 °C (ASTM D865-99)</u>		
	Hardness Change, pts.	+10(max)	+3
	Tensile Strength Change, %	-15(max)	+2
	Elongation Change, %	-25(max)	-5
	Weight Change, %		-0.2
<u>B36</u>	<u>Compression Set, 22 Hrs @ 150°C (ASTM D395-14, Method B)</u>	35%(plied)(max)	29.9
<u>EO16</u>	<u>IRM 901 Oil, 70 Hrs @ 150 °C (ASTM D471-12a)</u>		
	Hardness Change, pts.	-5~+10	+3
	Tensile Strength Change, %	-20(max)	+1
	Elongation Change, %	-30(max)	-14
	Volume Change, %	-10~+5	-3.3
<u>EO36</u>	<u>IRM 903 Oil, 70 Hrs @ 150 °C (ASTM D471-12a)</u>		
	Hardness Change, pts.	-15(max)	-6
	Tensile Strength Change, %	-40(max)	+2
	Elongation Change, %	-30(max)	-5
	Volume Change, %	+25(max)	+8.1
<u>F17</u>	<u>Low-Temperature Brittleness Point Test, 3 min at -40 °C (ASTM D2137-11, Method A)</u>		
	Sample type: T-50		
	Coolant : Isopropyl alcohol		
	Brittleness temperature to nearest 1°C	no crack	pass


Z1     Low Temperature Retraction Test (TR Test ) (ASTM D1329-08)

Testing Elongation 50%  
The Equipment of  
measure  
temperature:  
thermocouple  
Length of Sample: 51  
mm  
Rate of Temperature  
increasing: 1°C/min  
Test Temperature: 26 °C  
Coolant : Methanol

TR10, °C

-24.3

Statement and recommendation provided in this data sheet correspond to Ascend Sealing Technology's best knowledge on the subject at the date of its publication. The user should conduct their own analysis and testing and is solely responsible for making the final selection of the system and component. Since Ascend Sealing Technology cannot anticipate all the application parameters in actual conditions, we do not guarantee the results and assume no liability in connection with any use of this information.

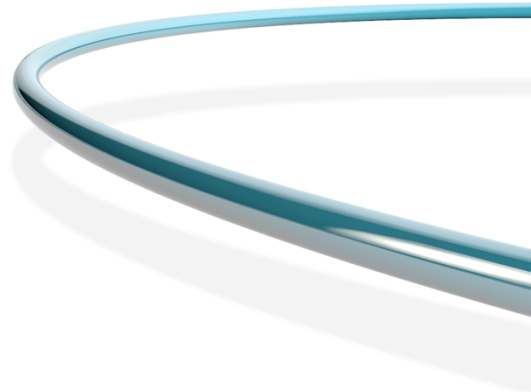

**Ascend Sealing Technology Inc.**

1211 Alderwood Ave, Sunnyvale, CA 94089  
Tel: (408) 962-0126 | Fax: (408) 962-0485  
Email: [customer\\_service@ascendsealing.com](mailto:customer_service@ascendsealing.com)  
<https://www.ascendsealing.com/>